

Evaluation of increase at the production of keratinolytics enzymes

Betina Galarza^{1,2}, Ivana Cavello^{1,2}, Laura Garro², Cecilia Gortari¹, Roque Hours¹, Carlos Cantera²

1.- CINDEFI (UNLP; CCT-La Plata, CONICET), 50 y 115, (1900) La Plata, Argentina

2.- CITEC (INTI-Cueros; CICPBA), Camino Centenario e/505 y 508, (1897) Manuel B. Gonnert, Argentina

betinagal@hotmail.com; icavello@biotec.org.ar

Introduction

The beamhouse area in leather technology has a notable influence on the gaseous and liquid effluent because they have to satisfy discharge standards. The organic matter content and the presence of suspended solids in the liquid effluent greatly depend on the unhairing process used: the conventional hair-burning unhairing, lime and sodium sulphide based, give the maximum values for beamhouse pollution.

Nowadays, conventional unhairing process employing lime and sulphide contribute 50-60% of total pollution load in terms of biochemical oxygen demand (BOD), chemical oxygen demand (COD), total dissolved solids (TDS) and total suspended solids (TSS) besides a high alkaline effluent of 100% toxicity. Hydrogen sulphide emanating from the unhairing process is proven to be fatal even in concentrations as low as 200 ppm. The extensive use of hazardous sulphide not only leads to unfavorable consequences for the environment but also undermines the efficacy of the effluent treatment plants. The pressure has increased and it has become common occurrence that tanneries are forced to close down not only in developed countries but also developing countries like China (Wang R et al. 2009). As compared with the classical sulphide unhairing method, a 50% reduction of sulphide was observed in the wastewater, as well as a 40% reduction in the suspended solid level. The decreased sulphide reduced odours and made it possible, by simple oxidation, to convert all the sulphide to sulphate giving the concentrations well below environmental specifications (Crispin et al. 2003).

The interest in the enzyme unhairing process trying to solve the difficulties that appear when intend to unhair only with enzymes without sodium sulphide. Difficulties are originated to the proteolysis, that cannot be controlled and thus the extension of enzyme activity towards the desired reticular structure of the dermis


cannot be avoided, notably impairing the properties of the elaborated leather.

Unlike the above difficulties present, attractive aspects are maintaining into the activities of research and development of enzyme unhairing, and not only confine their use in the soaking and bating process (Cantera et al 2000). In recent years enzyme applications has been extended to degreasing and wet-blue bating.

In special, enzymes for proteolytic depilation or keratin degradation are called keratinases (Riffel et al 2003). These enzymes act as proteases but differ from the non-keratinolytic proteases for their ability to degrade insoluble keratin (El Refai et al. 2005). They have a broad specificity proteolytic activity involving proteases of the endopeptidase type.

They have been purified and characterized from pancreas and different microorganisms such as some fungi, actinomycetes and bacteria genera. Some fungi, especially that belonging to Dermatophytes genera (Kunert, 2000; Simpanya, 2000) and others from fungi imperfecti (*Chrysosporium*, *Aspergillus*, *Alternaria*, *Trichuris*, *Curvularia*, *Cladosporium*, *Fusarium*, *Geomyces*, *Gleomastix*, *Paecilomyces*, *Scopulariopsis*, *Penicillium* and *Doratomyces* have been reported as a good producers of keratinolytic enzymes (Friedrich et al 1999).

Keratinases would be taking part in the so-called "sulphitolysis" process. During this mechanism the disulphide bond of the keratin breaks providing the sulphite ion that would act on the same kind of bond to generate thiosulphuric esters like S-sulfo-cysteine and thiols:

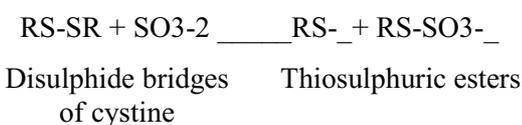

The sulphite ion reacts selectively with the S-S bond but it does not react with other amino acids residues except for the tryptophan (Yu et al. 1981).

As the culture medium lacks the sulphite ion, its synthesis must take place before sulphitolysis occurs. Little is known about the mechanism by which sulphites are formed in the early stages of keratinolysis. Proteolytic digestion and sulphitolysis are simultaneous and complementary phenomena which are used by microorganisms to transform keratin into nutritive material (Galarza et al 2004; Ruffin et al 1976).

Yates reported that the only enzymatic activity that may be related with depilation is a proteolytic one which involves proteases of the endopeptidase types (Yates 1968).

With regard to a casein substrate, a protein that was used in many research works as a depilatory activity marker it's appropriate to refer to Yates's work where the author finds that caseinolytic activity may be used to predict depilatory activity (Cantera et al 2004). In the present work casein substrate is replaced by azocasein, a diazotized aryl amine that produce a chromophoric derivative.

Keywords: Shaved, enzymes, tioglycolato, keratins, reducers.

Objectives

In the present work the enzymatic yields and proteic concentrations from crude extract of *Trichophyton ajelloi* growth in solid state cultures and submerged cultivation in the presence of reducing agents were determined.

Materials and methods

Isolation of fungus strain

The strain selected for this study *Trichophyton ajelloi*, was isolated from the soil of a Yak yard from La Plata Zoo using "Vanbreuseghem's hair baiting technique" (Vanbreuseghem 1952). This technique consists of incubating portions of nonsterile soil in Petri dish using keratin protein substrate upon which fungal growth is observed after two weeks of incubation in humid atmosphere. After isolation, the selected strain was kept in Sabouraud's agar at 28°C enriched with chloranphenicol used as antibacterial agent and cycloheximide to avoid the growth of environmental fungal growth. Reports

indicated that this species presents no pathogenesis for men or animals.

Culture conditions

Solid state culture

Assays were performed in Petri dishes containing 3 g of "hair waste" from "hair saving unhairing process" cleaned, autoclaved at 121°C for 15 min and ground (Galarza et al. 2007).

Innoculum preparation

The innoculum was prepared as follows: cultures of seven days in Sabouraud's Agar de *Trichophyton ajelloi* in 250 ml Erlenmeyers was resuspended with stir agitation in 10 ml water destilated aditionated with Tween 80. Then, 90 ml minimal mineral medium (MMM) with buffer $\text{NaH}_2\text{PO}_4\text{-K}_2\text{HPO}_4$ pH 7,2, chloranphenicol 0,5 g/l and trace amounts Cl_3Fe , Cl_2Zn and Cl_2Ca was added to suspension.

Then dishes were inoculated with 10 ml conidia suspension (fungal spores) whose viable-count was an average of 10^5 ufc/ml. In each experiment system the follows reducing agents were aditionated in final concentration 5 mM. 1) L-cistein hydrochloride monohydrate 2) sodium thioglycolate 3) sodium sulphite. In parallel, experiment system without reducing agent was made to compare the effect of reducing agent.

Incubation was done at 28°C in oven with humid atmosphere until 28 days. Two dishes were withdrawn every three days and stirred with 30 ml NaCl 0,5 N solution for 15 min to extract the enzymes adsorbed on solid substrates. The "crude extract" obtained was vacuum filtered through 0,45 μm cellulose membrane in an ice bath and kept at -20°C until used for protein and activity determination.

Submerged culture

Submerged cultures were carried out in 500 ml Erlenmeyers flasks using 200 ml of MMM with 1,0% (w/v) of "hair waste" treated as it described before. Reducer agent was added (duplicate) to flask in concentration 5mM, autoclaved for 15 min at 121°C, inoculated with 10 ml of inoculums. Flasks were incubated at 28°C, 200 rpm for 28 days,

withdrawing 5 ml of the culture every two days to obtain crude extracts. The samples were centrifugated at 3000xg for 15 min. The different extracts wer fractionates and kept at – 20°C until used.

Assessment of protein content and proteolytic activity

Protein concentration was determined by Bradford’s method (Bradford).

Assay of proteolytic activity

Enzyme activity was determined using azocasein (sulphamide azocasein) as substrate from Sigma Chem.Co., St. Louis, MO. Reaction mixture containing 100 µl of crude extract and 250 µl of the 1% (w/v) substrate solution in 0,1 M Tris-HCl buffer pH 9 was incubated for 30 min a 37°C and then stopped by the addition of 1 ml of tricloroacetic acid

(TCA) 10% (w/v) and centrifuged (3000xg, 15 min). One ml of NaOH was added to 0,9 ml of the supernatant, agitated and measured at 440 nm (triplicate). Blank was performed using enzyme solution inactivated for heating at 100°C 5 min.

Azocasein activity unit (Uc) is defined as the amount of enzyme that, under the test conditions causes an increase of 0,1 Abs440 per minute..

Results and discussion

Los siguientes gráficos representan: I y III: actividad azocaseinolítica en función de los días de cultivo en ambos medios (sólido y líquido sumergido) respectivamente; II y IV: la concentración proteica en función de los días de cultivo en ambos medios (sólido y líquido sumergido) respectivamente.

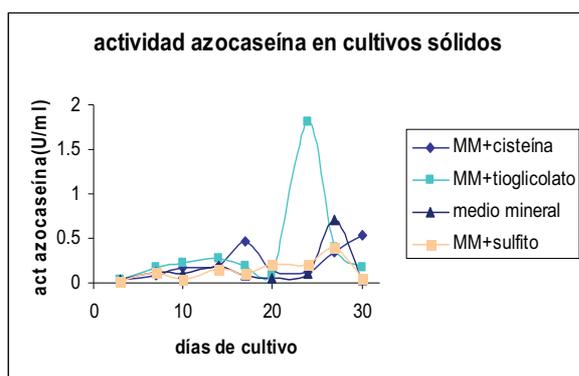


Gráfico I

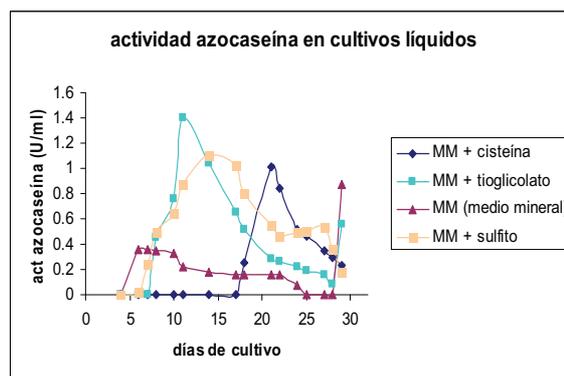


Gráfico III

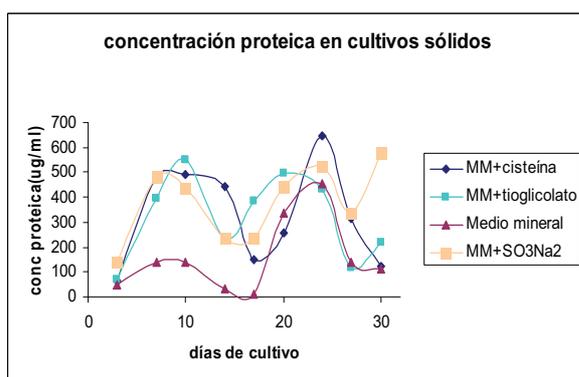


Gráfico II

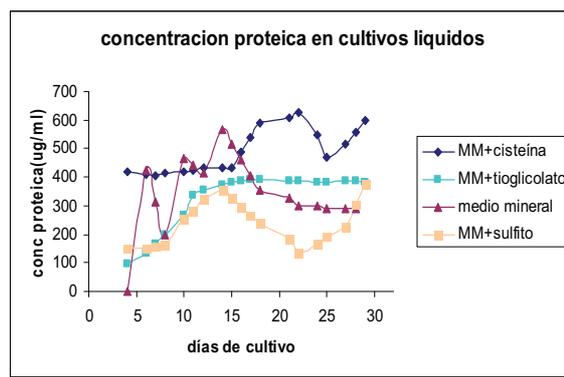


Gráfico IV

The follows graphics represents: I and III: azocaseinolytic activity as a function of day of culture in both, solid and submerged medium; II and IV: proteic concentration as function of day of culture in both, solid and submerged

medium. It can be observed in graphics of proteic concentration vs days of culture, in both, solid and submerged cultura the highest values were after cystein addition. For azocaseinolytic activity, sodium thioglycolate

in submerged culture produced a maximum on day 11. This value exceeded in 7 times those produced by mineral medium addition for the same day. In solid culture the highest point of activity was on 24 day for sodium thioglycolate. This is the same rise than the previous (submerged culture) in comparison with mineral medium without aggregates.

Conclusions

It is possible to conclude that the aggregate of reducing agents to culture medium, in special sodium thioglycolate, increases the production of keratinolytic enzymes.

This finding can be explained taking account the sulphitolysis process.

In special case of *Trichophyton ajelloi*, sodium thioglycolate was used as reducing agent and

The absolute values of the points of azocaseinolytic activity for solid culture were always higher than submerged culture while the highest proteic concentrations values were similar in both types of cultures. *similares en ambos tipos de cultivo.*

as sole carbon energy source while cystein is besides incorporated as nitrogen source.

This action show a potential use of keratinases in tannery process as: soaking, unhairing, bating and deliming and adds value to the tannery solid waste as hair waste in process related with the bioconversion into feed and fertilizers..

References

Bradford (1976) "A rapid and sensitive method for the quantitation of microgram quantities of protein utilizing the principle of protein-dye binding". *Analytical Biochemistry* 72 (248-254).

Cantera C, Garro ML, Goya L, Barbeito C, Galarza B (2004) "Hair saving unhairing process: part 6. Stratum corneum as a diffusion barrier: chemical-mechanical injury of epidermis". *Journal of the Society of Leather Technologists and chemists*, Vol 88 (121-131).

Cantera C (2000) "Hair saving unhairing process. Part 4. Remarkes on the evolution of the investigations on enzyme unhairing". *Journal of the Society of Leather Technologists and chemists*, Vol.85 (125-132).

Crispim A, Mota M (2003) "Unhairing with enzymes". *Journal of the Society of Leather Technologists and chemists*, Vol 87 (198-202).

El Refai HA, AbdelNany MA, Gaballa A, El-Araby MH, Abdel Fattah AF (2005) "Improvement of the newly isolated *Bacillus pumilus* FH9 keratinolytic activity". *Process Biochemistry*, 40 (2325-2332).

Friedrich J, Gradisar H, Mandin D, Chaumont JP (1999) "Screening fungi for synthesis of keratinolytic enzymes". *Letters in Applied Microbiology* 28 (127-130).

Galarza BC, Goya L, Cantera C, Garro ML, Reinoso H, López L (2004) "Fungal biotransformation of bovine hair. Part 1: Isolation of fungus with keratinolytic activity". *Journal of the Society of Leather Technologists and chemists*, Vol 88 (93-98).

Galarza BC, Garro ML, Cavello I, Cazau MC, Hours R, Cantera CS (2007) "Fungal biotransformation of bovine hair: assessment of structural changes". *Journal of the Society of Leather Technologists and chemists*, Vol 91 (229-232).

Kunert, J (2000) "Physiology of keratinophilic fungi". Libro editado por la Revista Iberoamericana de Micología, Ed. RKS Kushwaha & Guarro J, Bilbao. ISBN 84-607-0711-3, cap 10 (77-85).

Riffel A, Ortolan S, Brandelli A (2003) "De-hairing activity of extracellular proteases produced by keratinolytic bacteria". *Journal Chemical Technology and Biotechnology*, 78 (855-859).

Ruffin P, Andrieu S, Biserte G (1976) "Sulphitolysis in keratinolysis. Biochemical proof". *Sabouradia*, 14 (181-184).

Simpanya M (2000) "Dermatophytes: Their taxonomy, ecology and pathogenicity". *Revista Iberoamericana de Micología*, (1-12)

Vanbreuseghem, R (1952) "Technique biologique pour l'isolement des dermatophytes du sol". *Annales Société Belgique Médecine Tropical* 32 (173-178).

Wang R, Min C, Haiming C, Li Z. (2009) "Enzyme unhairing-an eco friendly biotechnological process". *Journal of the Society of Leather Technologists and chemists*, Vol 93 (51-55).


Yates J (1968) "Studies in depilation. VI. Correlation of activity of depilatory enzyme systems with their activity against simple substrates". *Journal American Leather Chemist Association* .63 (474)

Yates J (1972) "Studies in depilation. Part X. The mechanism of the enzyme depilation process". *Journal of the Society of Leather Technologists and chemists*. 56 (158-175).

Yu M, Torchinsky S (1981) "Sulfur in Proteins". Pergamon Press Ltd, Headington Hill Hall, Oxford OX3 OBW, England, 1^o ed.

Acknowledgements

This research work was supported by Scientific Research Commission of the Province of Buenos Aires (CICPBA), National Institute of Technology (INTI) and National Council of Research and Technology (CONICET), Argentine.

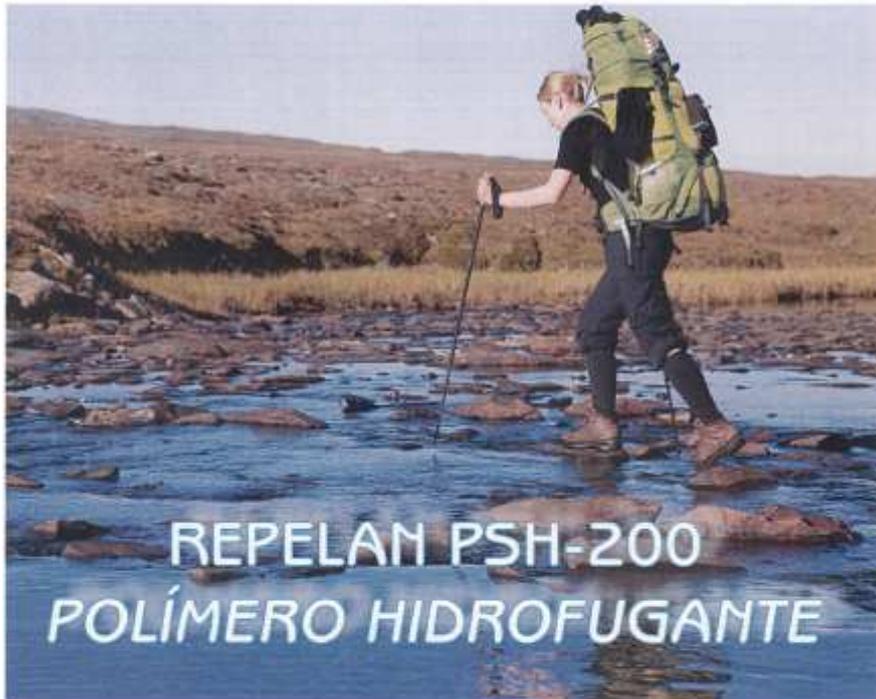

REPELAN PSH-200 POLÍMERO HIDROFUGANTE

- ▲ Especialmente diseñado para cueros hidrofugados con altos requerimientos en el test Maeser.
- ▲ Se fija con curtientes minerales.
- ▲ Tinturas igualadas.
- ▲ Tacto agradable y excelente plenitud.



CROMOGENIA-UNITS, S.A.

Farell, 9 - 08014 Barcelona (Spain)
Tel. (34) 93 432 94 00
Fax (34) 93 422 60 14
E-mail: cromogenia@cromogenia.com
www.cromogenia.com

0218

